

# 1



## Environmental Product Declaration **Softwood Timber**



Environmental Product Declaration (EPD)  
in accordance with ISO 14025 and EN 15804

EPD Registration No. S-P-00560 | Version 2.0  
Issued 23 June 2015 | Revised 14 Feb 2022 | Valid until 14 Feb 2027

Geographical Scope: Australia





## Environmental Product Declarations

WoodSolutions has developed a suite of EPDs for industry-average, Australian-produced timber products.

These EPDs help to showcase the environmental credentials of Australian wood products. They also provide life cycle data for calculating the impacts of wood products at a building level.

EPDs include:

- #01 Softwood Timber**
- #02 Hardwood Timber**
- #03 Particleboard**
- #04 Medium Density Fibreboard (MDF)**
- #05 Plywood**
- #06 Glued Laminated Timber (Glulam)**
- #07 White Cypress Timber**

WoodSolutions is an industry initiative designed to provide independent, non-proprietary information about timber and wood products to professionals and companies involved in building design and construction.

WoodSolutions is resourced by Forest and Wood Products Australia (FWPA). It is a collaborative effort between FWPA members and levy payers, supported by industry peak bodies and technical associations.

This work is supported by funding provided to FWPA by the Commonwealth Government.

978-1-925213-19-5

### Researchers:

thinkstep Pty Ltd,  
25 Jubilee Street, South Perth WA 6151, Australia

### Version history

**V1.0** Initial version based on 2005/06 data from CSIRO and produced by thinkstep Pty Ltd and the Timber Development Association (NSW) Ltd.

**V1.1** Minor corrections to text and images in V1.0.

**V1.2** Revised version incorporating 2015/16 data from a new industry survey, as well as updates to Global Warming Potential (GWP) and fresh water indicators.

**V1.3** - Revised version for correction of the validity period, documentation of the forestry carbon modelling assumptions and correction of minor typographical errors.

**V2.0** - New version incorporating data for 2019-20 production year from a new industry survey, updated methane recovery from landfill, updated text, and references.

Produced: February 2022

© 2022 Forest and Wood Products Australia Limited. All rights reserved.

These materials are published under the brand WoodSolutions by FWPA.

### IMPORTANT NOTICE

Forest & Wood Products Australia has sole ownership, responsibility, and liability for this EPD.

This publication provides general information only and is no substitute for professional technical advice. Users must make their own determination as to the suitability of this information or any product covered by this publication for their specific circumstances. Forest and Wood Products Australia Ltd accepts no liability for any loss or damage resulting from their specific circumstances. Forest and Wood Products Australia Ltd accepts no liability for any loss or damage resulting from any reliance on the information provided in this publication.

The work is copyright and protected under the terms of the Copyright Act 1968 (Cwth). All material may be reproduced in whole or in part, provided that it is not sold or used for commercial benefit and its source (Forest & Wood Products Australia Limited) is acknowledged and the above disclaimer is included. Reproduction or copying for other purposes, which is strictly reserved only for the owner or licensee of copyright under the Copyright Act, is prohibited without the prior written consent of FWPA.

WoodSolutions Australia is a registered business division of Forest and Wood Products Australia Limited.

# EPD Details

An Environmental Product Declaration, or EPD, is a standardised and verified way of quantifying the environmental impacts of a product that is based on a consistent set of rules known as a PCR (Product Category Rules).

EPDs within the same product category from different programs may not be comparable. EPDs of construction products may not be comparable if they do not comply with EN 15804.

Forest & Wood Products Australia has sole ownership, responsibility, and liability for this EPD.

## Declaration owner:

### Forest and Wood Products Australia Ltd

Web: [www.fwpa.com.au](http://www.fwpa.com.au)

Email: [info@fwpa.com.au](mailto:info@fwpa.com.au)

Post: Level 11, 10-16 Queen Street, Melbourne VIC 3000, Australia



## EPD produced by:

### thinkstep Pty Ltd

Web: [www.thinkstep-anz.com](http://www.thinkstep-anz.com)

Email: [anz@thinkstep-anz.com](mailto:anz@thinkstep-anz.com)

Post: 25 Jubilee Street, South Perth WA 6151, Australia



## EPD program operator:

### EPD Australasia Limited

Web: [www.epd-australasia.com](http://www.epd-australasia.com)

Email: [info@epd-australasia.com](mailto:info@epd-australasia.com)

Post: EPD Australasia Limited, 315a Hardy Street  
Nelson 7010, New Zealand



## CEN standard EN15804+A1 served as the core PCR

### PCR:

PCR 2012:01 Construction products and Construction services, Version 2.33, 2020-09-18

### PCR review was conducted by:

The Technical Committee of the International EPD® System.

Chair: Massimo Marino. Contact via [info@environdec.com](mailto:info@environdec.com).

### Independent verification of the declaration and data, according to ISO 14025:

- EPD process certification (Internal)
- EPD verification (External)

## Third party verifier

### Kimberly Robertson, Catalyst Ltd

Web: [www.catalystnz.co.nz](http://www.catalystnz.co.nz)

Email: [kimberly.robertson@catalystnz.co.nz](mailto:kimberly.robertson@catalystnz.co.nz)



### Verifier approved by: EPD Australasia Ltd

### Procedure for follow-up of data during EPD validity involves third-party verifier:

- Yes
- No

# Introduction

This Environmental Product Declaration presents the average performance of sawn timber from Australian grown softwood processed in Australia by members of Forest and Wood Products Australia (FWPA). It recognises the importance of transparency by providing information on the raw materials, production and environmental impacts of Australian softwood.

This EPD has been prepared in accordance with ISO 14025:2006, EN 15804:+A1 and PCR 2012:01 (IEPDS 2020). It covers Australian seasoned softwood products produced in accordance with the following standards:

- AS/NZS 1748 Timber – Mechanically stress-graded for structural purposes
- AS 2858 Timber – Softwood – Visually stress-graded for structural purposes
- AS 4785 Timber – Softwood – Sawn and milled products.

The environmental data presented in this document are primarily derived from a survey of industry members covering production in the 2019-20 financial year conducted by thinkstep-anz on behalf of FWPA. This is an update of an earlier survey conducted by thinkstep-anz based on production in the 2015-16 financial year, which was used in the previous version of this EPD. The current survey covers over 40% of total sawn softwood production in Australia.

Production of this EPD has been facilitated by FWPA and Australian Forest Products Association (AFPA) with participation of current sawn softwood timber producer members of FWPA listed in Table 1. All FWPA members have contributed financially through levies paid to FWPA and some have also contributed data (as shown in Table 1).

**Table 1: FWPA members contributing to this EPD.**

Sawn softwood producer company name	Financial contributor	No. of sawmills contributing data 2020
Allied Timber Products Pty Ltd	X	
Associated Kiln Driers Pty Ltd trading as A.K.D. Softwoods	X	2
Australian United Timbers Pty Ltd	X	
Auswest Timbers Pty Ltd	X	
Pentarch Forestry	X	
Carter Holt Harvey Woodproducts Australia <sup>1</sup>	X	
D&R Henderson Pty Ltd	X	
Highland Pine Products Pty Ltd <sup>2</sup>	X	
Hyne Timber	X	1
KSI Sawmills Pty Ltd	X	
LM Hayter & Sons Pty Ltd	X	
Lorimer Timber Pty Ltd trading as Davids Timber	X	
McDonnell Industries Pty Ltd trading as NF McDonnell & Sons	X	
OneFortyOne Plantations Pty Ltd	X	1
Penrose Pine Products Pty Ltd	X	
Rodpak Pty Ltd	X	
SA Sawmilling Pty Ltd	X	
Tarmac Sawmilling Pty Ltd	X	
TASCO trading as Dongwha Timbers Pty Ltd	X	
Timberlink Australia	X	2
Wespine Industries Pty Ltd	X	1
Whiteheads Timber Sales Pty Ltd	X	

<sup>1</sup> Not a softwood manufacturer in 2020 <sup>2</sup> Joint venture of AKD Softwoods and Pentarch Forestry

## Description of the Australian Sawn Softwood Industry

The Australian softwood manufacturing industry is an important contributor to the Australian economy – particularly to the regional economies where many producers are based. In 2017-18 it is estimated that 76,200 people were employed in all forestry, logging, and wood manufacturing categories, with forestry and forest product manufacturing contributing 0.5% of Australia's GDP (ABARES 2019).

In 2018-19, the industry produced 3.3 million cubic metres of sawn softwood timber products (excluding cypress pine) (based on the 2018-19 total from Gavran 2020 as adjusted to saleable volume following Houghton 2015). There are 58 softwood sawmills manufacturing sawn softwood across Australia – see Table 2. Production is dominated by large sawmills, 20 of which have a log input capacity greater than 100,000 m<sup>3</sup> per year (Downham et. al. 2019).


**Table 2: Softwood sawmills by Australian state**

NSW <sup>a</sup>	Vic.	QLD	SA	WA & Tas <sup>b</sup>	Aust.
14	9	17	13	5	58

*a Includes ACT*

*b includes Northern Territory.*

*Source: ABARES 2019*

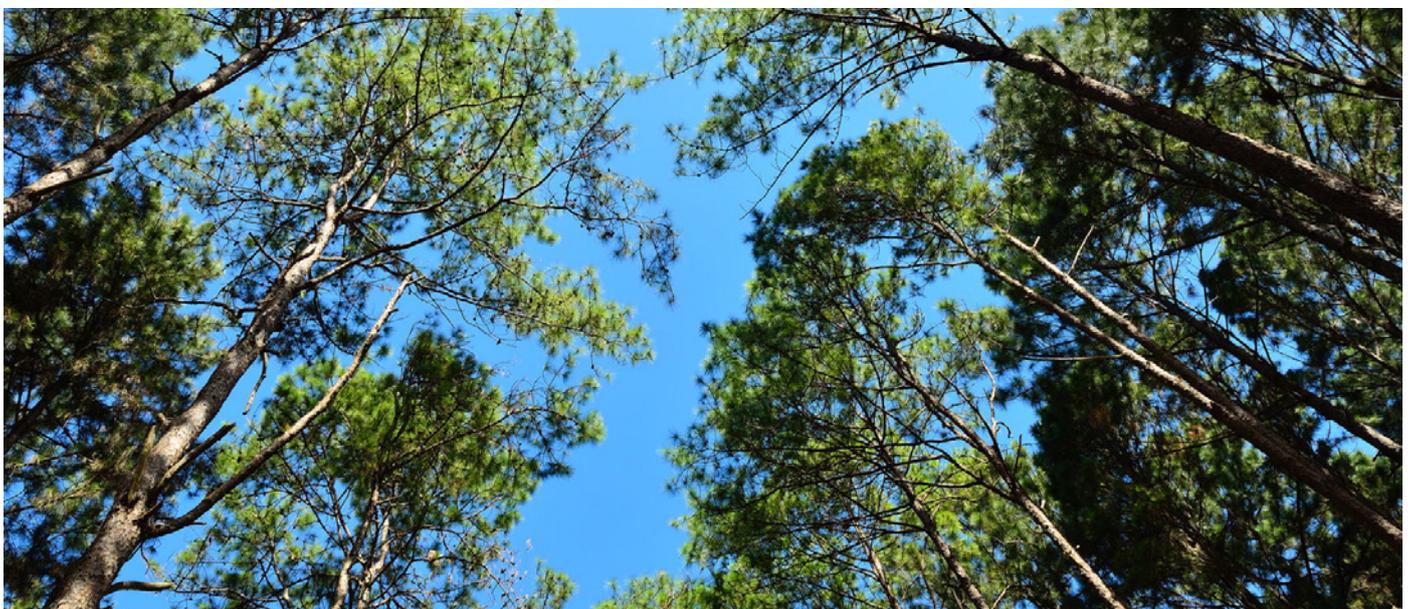

## Description of Sawn Softwood Products

Seasoned sawn softwood is widely used in residential and multi-residential frame construction (wall frames: studs, plates, headers; floor and roof truss components) and other internal fit-out elements (see Table 3).

Structural grade seasoned softwood is usually sold with a dressed surface finish (planer gauged). It may also be rougher headed, which is a reeded finish. Structural softwood is also available preservative treated (see Other Environmental Information section) for a variety of internal (termite protected) and external (termite and decay protected) applications. Factory manufactured finger-jointed and metal plate connector joined products are also available.

Appearance grade seasoned softwood is usually sold for internal fit-out elements such as mouldings, wall and ceiling linings, furniture, cladding and flooring.

**Table 3: Proportion of Australian softwood by product group (2019-20).**

**Source: FWPA Softwood Timber Survey 2021**

Softwood product	% of total
Outdoor Domestic	8.9%
Appearance	0.5%
Outdoor Other	9.2%
Structural Untreated	26.1%
Structural H2 and H2F	22.6%
Packaging	19.9%
Ungraded	9.0%
Export	3.7%
<b>Total</b>	<b>100%</b>



Image courtesy of Hyne Timber



Image courtesy of FWPA



Image courtesy of Timberlink Australia



Image courtesy of Timberlink Australia

Seasoned sawn softwood timber is sold by grades for strength or appearance and the quantity specified by cross section and lineal metres. Although it is possible to cut timber to a large range of cross sections, there are a number of common dimensions for the dominant building products such as timber studs for floor, wall and roof framing (see Table 4 and Table 5).

**Table 4: Structural grades of seasoned sawn softwood and availability. Source: WPV 2009**

Typical species	Stress grade	Supply
Radiata Pine, Hoop Pine, Slash Pine, Maritime Pine, Caribbean Pine	F5	Readily available
	F7	Available from selected suppliers
	MGP10	Readily available
	MGP12	Available from selected suppliers
	MGP15	Available from selected suppliers

**Table 5: Structural seasoned softwood - available sizes. Source: WPV 2009.**

Breadth (mm)	Depth (mm)							
	42	70	90	120	140	190	240	290
35	X	Y	Y	Y	Y	Y	X	X
45		Y	Y	Y	Y	Y	Y	Y
90			X					

Key: X = Available from selected suppliers; Y = Readily available

## Use of EPDs in Green Star and Sustainable Infrastructure Rating Systems

### Green Star

This document complies with the requirements for an industry or sector wide EPD under the Green Building Council of Australia’s Green Star rating system given that:

- It conforms with ISO 14025 and EN 15804.
- It has been verified by an independent third party.
- It has at least a cradle-to-gate scope.
- The participants in the EPD are listed (see Table 1).

Additional points may be applicable under the Responsible Products Framework currently under development.

### IS® Rating

This EPD complies with requirements under the Infrastructure Sustainability Council’s IS® rating scheme given that it is:

- Compliant with ISO 14025 and EN15804
- Verified by a third party.

## Products

This Sector EPD describes the following average products (declared units) manufactured in Australia by the FWPA members listed in Table 1:

- 1 m<sup>3</sup> of sawn kiln-dried softwood  
12% moisture content (dry basis), density of 551 kg/m<sup>3</sup>
- 1 m<sup>3</sup> of dressed kiln-dried softwood  
12% moisture content (dry basis), density of 551 kg/m<sup>3</sup>

The declared units above represent an entire product category rather than a specific product from a specific manufacturer. The values represent a production volume weighted average. As such, a specific product purchased on the market may have a lesser or greater environmental impact than the average presented in this EPD. Some products may also undergo further processing (e.g. fabrication into frames and trusses) before being used in a building.

All wood used in these products is from Australian native and exotic (non-native) softwood species grown in plantations. The dominant softwood species used to produce sawn timber in Australia is *Pinus radiata* (radiata pine). Other softwood species used are *Araucaria cunninghami* (hoop pine), *Pinus pinaster* (maritime pine) and the Southern Pines: *Pinus elliottii* (slash pine), *Pinus caribaea* (Caribbean pine) and hybrids thereof.

The results in the main body of this EPD are for untreated timber. Information on treatment can be found in the Additional Environmental Information section. The results for the specific treatment type used can be added to the results for untreated timber to calculate the environment profile for treated timber.

Table 6 indicates the availability of softwood by hazard class (a bold **X** indicates a common product).

**Table 6: Availability of softwood by hazard class**

Products	Untreated	H1	H2/H2F	H3	H4	H5	H6
Softwood, rough sawn, kiln-dried	<b>X</b>			<b>X</b>	<b>X</b>	X	
Softwood, dressed, kiln-dried	<b>X</b>		<b>X</b>	X	X		

## End Uses

<b>Sawn kiln-dried softwood</b>	Packaging, outdoor domestic and fencing (after appropriate treatment)
<b>Dressed sawn kiln-dried softwood</b>	Structural framing, utility, H2F structural framing, mouldings, architraves, joinery, furniture, flooring grades

## Representativeness

**Market coverage:** The data in this EPD are from detailed surveys of 7 of the 29 softwood mills in Australia which are operated by FWPA members. These 7 mills collectively processed 3,963,271 m<sup>3</sup> softwood saw logs in 2019/20, equating to 41.1% of total harvest of approximately 9,651,000 m<sup>3</sup> of saw logs (based on the 2019/20 total from Gavran 2020 for softwood logs, excluding cypress, veneer, pulp and other logs) and approximately 45.6% of total softwood saw log inputs by FWPA sawn softwood producer members (assuming FWPA members account for 90% of Australian production).

**Temporal representativeness:** Primary data were collected from participating sites for the 2019/20 Australian financial year (1st July 2019 to 30th June 2020). Following EN 15804, site-specific data are valid for 5 years (to 30th June 2025), meaning that these datasets are valid until the end of this EPD's validity period.

**Geographical and technological representativeness:** The data are representative of the 7 sites surveyed, which collectively produce over 40% of all Australian-produced sawn softwood. More detailed information can be found in the Variation in Results section later in this EPD.

## Industry Classifications

Product	Classification	Code	Category
All	UN CPC Ver.2.1	31101	Wood, sawn or chipped lengthwise, sliced or peeled, of a thickness exceeding 6 mm, of coniferous wood
All	ANZSIC 2006	1413	Timber resawing and dressing

# LCA Calculation Rules

## System Boundary

This EPD is of the 'cradle-to-gate' type with options. The options include the end-of-life stage, which is modelled through the use of scenarios.


Product stage			Con- struction process stage		Use stage							End-of-life stage				Benefits and loads beyond the system boundary
Raw material supply	Transport of raw materials	Manufacturing	Transport to customer	Installation	Use	Maintenance	Repair	Replacement	Refurbishment	Operational energy use	Operational water use	Deconstruction / demolition	Transport to waste processing	Waste processing	Disposal	Reuse- Recovery- Recycling- potential
A1	A2	A3	A4	A5	B1	B2	B3	B4	B5	B6	B7	C1	C2	C3	C4	D
X	X	X	MND	MND	MND	MND	MND	MND	MND	MND	MND	MND	MND	X	X	X

Key: X = included in the EPD

MND = module not declared (such a declaration shall not be regarded as an indicator result of zero)

## Production

The production stage includes the forestry, sawmilling and kiln drying stages for all products and planing for dressed timber. Preservative treatment has been included separately to timber production within this EPD. Environmental profiles for a range of common treatment options are included in the Durability and Preservative Treatment section within this EPD.

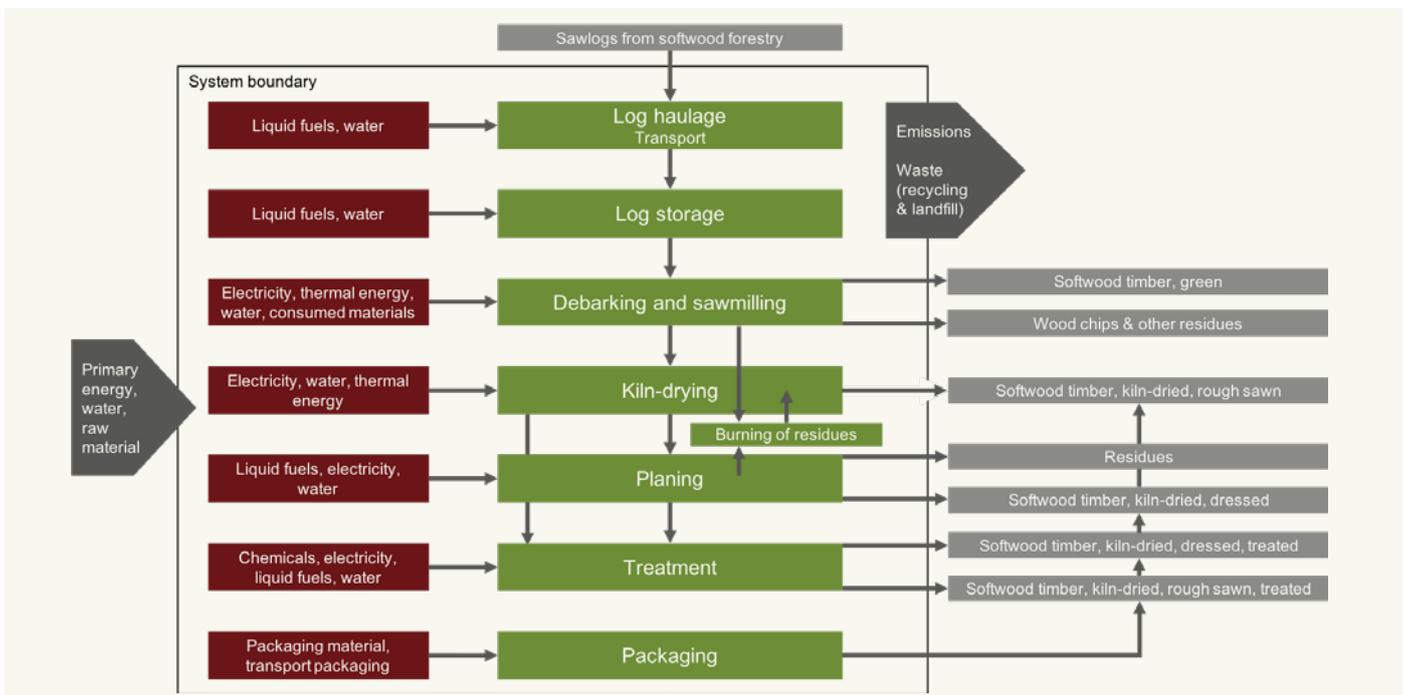

When a wood product reaches the end of its useful life, it may either be reused, recycled, landfilled or combusted to produce energy. Landfill is currently the most common end-of-life route for wood products in Australia. With the exception of reuse, which is not common for softwood, all other scenarios are in use in certain regions (Forsythe Consultants 2007; National Timber Product Stewardship Group) and have been included within this EPD.

Each scenario assumes that 100% of the wood is sent to that scenario. To create an end-of-life mix for a given region or end use, the reader should take a weighted sum of these scenarios. Where no data are available, the 'landfill (typical)' scenario should be used for 100% of the waste.

### Landfill

This EPD includes two scenarios for landfill, each with a different value for the degradable organic carbon fraction (DOC<sub>f</sub>) of wood. The two values are based on bioreactor laboratory research. This experimental work involves the testing of a range of waste types in reactors operated to obtain maximum methane yields. As the laboratory work optimises the conditions for anaerobic decay, the results can be considered as estimates of the DOC<sub>f</sub> value that would apply over very long time horizons (Australian Government 2014a, p.17).

- **Landfill (typical):** DOC<sub>f</sub> = 0.1%. This is based on bioreactor laboratory research by Wang *et al.* (2011) on radiata pine timber, the dominant softwood species in Australia.
- **Landfill (NGA):** DOC<sub>f</sub> = 10%. This is the value chosen for Australia's National Greenhouse Accounts (NGA) (Australian Government 2020). This is a reduction from the previous value of 23% (Australian Government 2014b) that was derived from early bioreactor laboratory research from the 1990s (e.g. Barlaz 1998) that investigated the degradability of wood tree branches ground to a fine powder under anaerobic conditions (Australian Government 2014a, p.17). This DOC<sub>f</sub> value can be considered extremely conservative when compared to values from later research (as used in the typical scenario above) and effectively assumes that at least part of the wood waste is ground into a powder to accelerate degradation.

The impacts associated with the landfill are declared in module C4. All landfill gas that is combusted for energy recovery (module C4) is assumed to occur in a power plant with an electrical conversion efficiency of 36% (Australian Government 2014b, p.189) and the resulting electricity receives a credit for offsetting average electricity from the Australian grid (module D) in line with EN 16485:2014 (Section 6.3.4.5).

Both landfill scenarios assume the following for carbon emissions:

- Of the gases formed from any degradation of wood in landfill, 50% is methane and 50% is carbon dioxide (Australian Government 2020, Table 46).
- All carbon dioxide is released directly to the atmosphere.
- 43% of the methane is captured, based on weighted average methane captured in Australian landfills (Australian Government 2021).
- Of this 43% captured, one-quarter (10.8% of the total) is flared and three-quarters (32.3% of the total) are used for energy recovery (Carre 2011).
- Of the 57% of methane that is not captured, 10% (5.7% of the total) is oxidised (Australian Government 2016, Table 43) and 90% (51.3%) is released to the atmosphere.
- In summary, for every kilogram of carbon converted to landfill gas, 74.4% is released as carbon dioxide and 25.7% is released as methane.

## Energy recovery

This scenario includes shredding (module C3) and combustion with recovered energy offset against average thermal energy from natural gas (module D) in line with EN 16485:2014 (Section 6.3.4.5). Note that other options are also in use within Australia, including replacement of coal, replacement of electricity, and replacement of both electricity and thermal energy (via co-generation). The modelling assumes that the product waste has value after it has been sorted.

## Recycling

Softwood may be recycled in many different ways. This scenario considers shredding and effectively downcycling into wood chips. Wood waste is chipped (module C3) and assigned credits relative to the avoided production of woodchips from virgin softwood (module D). The CO<sub>2</sub> sequestered and the energy content of the wood are assumed to leave the system boundary at C3 so that future product systems can also claim these without double-counting (EN 16485:2014, Section 6.3.4.2).

## Key Assumptions

**Energy:** Thermal energy and transport fuels have been modelled as the Australian average (see Sphera 2020 for documentation). Electricity for production (modules A1-A3) has been modelled as a state-specific split based upon the volume of production in each state for the 2018-19 financial year (the most recent year split by state in Gavran, 2020): 30% NSW, 23% VIC, 18% SA, 15% QLD, 8% TAS, 6% WA. Electricity at end-of-life (module C) has been modelled using an average Australian electricity mix as the location where the product reaches end-of-life is unknown.

**Forestry:** All breakdown of forest matter after harvest is modelled as aerobic and therefore carbon neutral as carbon sequestered is released as carbon dioxide. Any burning of forestry material left behind after logging is modelled as being carbon neutral, aside from the trace emissions of various organic gases (Commonwealth of Australia, 2016). All forestry is assumed to be sustainably managed and as such there are no carbon emissions associated with land use change. Loss of carbon from the soil is assumed to be zero (i.e. no significant erosion). Wildfires are relatively rare in softwood plantations, but can be locally significant over short time periods. Carbon losses (and emissions) from fire are balanced by carbon gains (and sequestration) from regrowth. It is therefore better to review data over a longer-term horizon of several years.

Table 5.3 of Australia's State of the Forest Report 2018 (SOFR) (ABARES, 2018) reports net carbon losses/gains in softwood plantations from fire and regrowth from fire as 0.0 Mt over 2011-16 and -0.1Mt (so a release of 0.1 Mt of carbon) over the period 2001-16. CO<sub>2</sub> emissions from the 2001-16 period have been incorporated into this study. This report does not include calculations of other greenhouse gases emitted during forest fires as there is insufficient data however these are minor compared to CO<sub>2</sub> emissions.

## Cut-off Criteria

Environmental impacts relating to personnel, infrastructure, and production equipment not directly consumed in the process are excluded from the system boundary as per the PCR (IEPDS 2020, Section 7.5.4). All other reported data were incorporated and modelled using the best available life cycle inventory data.

## Allocation

**Upstream data:** For refinery products, allocation is done by mass and net calorific value. Inventories for electricity and thermal energy generation include allocation by economic value for some by-products (e.g. gypsum, boiler ash and fly ash). Allocation by energy is applied for co-generation of heat and power. For materials and chemicals, the allocation rule most suitable for the product is applied (see Sphera 2020).

**Co-products (e.g. sawn wood and sawdust from milling):** As the difference in economic value of the co-products is high (>25% as per EN 15804, Section 6.4.3.2), allocation has been done by economic value.

## Background Data

Data for all energy inputs, transport processes and raw materials are from GaBi Databases 2020 (Sphera 2020). Most datasets have a reference year between 2016-2019 and all fall within the 10-year limit allowable for generic data under EN 15804 (Section 6.3.7).

# EPD Results

Note: these tables show the impacts associated with production and end-of-life. Any potential credits to future products from recycling or energy recovery are presented in the Other Environmental Information section.

## Environmental Impact Indicators

An introduction to each environmental impact indicator is provided below. The best-known effect of each indicator is listed to the right of its name.

### Global Warming Potential (GWP) → Climate Change

A measure of greenhouse gas emissions, such as carbon dioxide and methane. These emissions increase absorption of radiation emitted by the earth, intensifying the natural greenhouse effect. Contributions to GWP can come from either fossil or biogenic sources, e.g. burning fossil fuels or burning wood. GWP is reported as a total as well as being separated into biogenic carbon (GWPB) and fossil carbon (GWPF).



### Ozone Depletion Potential (ODP) → Ozone Hole

A measure of air emissions that contribute to the depletion of the stratospheric ozone layer, causing higher levels of ultraviolet B (UVB) to reach the earth's surface with detrimental effects on humans, animals and plants.



### Acidification Potential (AP) → Acid Rain

A measure of emissions that cause acidifying effects to the environment. Acidification potential is a measure of a molecule's capacity to increase the hydrogen ion (H+) concentration in the presence of water, thus decreasing the pH value. Potential effects include fish mortality, forest decline and the deterioration of building materials.



### Eutrophication Potential (EP) → Algal Blooms

A measure of nutrient enrichment that may cause an undesirable shift in species composition and elevated biomass production in both aquatic and terrestrial ecosystems. It includes potential impacts of excessively high levels of macronutrients, the most important of which are nitrogen (N) and phosphorus (P).



### Photochemical Ozone Creation Potential (POCP) → Smog

A measure of emissions of precursors that contribute to ground level smog formation (mainly ozone O<sub>3</sub>), produced by the reaction of VOCs and carbon monoxide in the presence of nitrogen oxides under the influence of UV light. Ground level ozone may be harmful to human and ecosystem health and may also damage crops.



### Abiotic Depletion Potential (ADP) → Resource Consumption

The consumption of non-renewable resources leads to a decrease in the future availability of the functions supplied by these resources. Depletion of mineral resource elements (ADPE) and non-renewable fossil energy resources (ADPF) are reported separately.



**Table 7: Environmental impacts, 1 m<sup>3</sup> of sawn, kiln-dried softwood.**

	Production	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
Parameter [Unit]	A1-A3	C4	C4	C3	C3
GWP [kg CO <sub>2</sub> -eq.]	-764	57.9	364	906	906
GWPF [kg CO <sub>2</sub> -eq.]	117	56.6	56.8	5.58	5.58
GWPB [kg CO <sub>2</sub> -eq.]	-881	1.28	307	900	900
ODP [kg CFC11-eq.]	1.80E-13	1.99E-13	1.99E-13	9.87E-16	9.87E-16
AP [kg SO <sub>2</sub> -eq.]	0.740	0.170	0.196	0.0352	0.0352
EP [kg PO <sub>4</sub> <sup>3-</sup> -eq.]	0.209	0.0203	0.0267	0.00818	0.00818
POCP [kg C <sub>2</sub> H <sub>4</sub> -eq.]	0.594	0.0106	0.0684	0.00306	0.00306
ADPE [kg Sb-eq.]	7.17E-05	4.70E-06	4.70E-06	6.86E-08	6.86E-08
ADPF [MJ]	1,430	814	814	73.8	73.8

**Table 8: Environmental impacts, 1 m<sup>3</sup> of dressed, kiln-dried softwood.**

	Production	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
Parameter [Unit]	A1-A3	C4	C4	C3	C3
GWP [kg CO <sub>2</sub> -eq.]	-718	57.9	364	906	906
GWPF [kg CO <sub>2</sub> -eq.]	157	56.6	56.8	5.58	5.58
GWPB [kg CO <sub>2</sub> -eq.]	-875	1.28	307	900	900
ODP [kg CFC11-eq.]	2.24E-13	1.99E-13	1.99E-13	9.87E-16	9.87E-16
AP [kg SO <sub>2</sub> -eq.]	0.963	0.170	0.196	0.0352	0.0352
EP [kg PO <sub>4</sub> <sup>3-</sup> -eq.]	0.263	0.0203	0.0267	0.00818	0.00818
POCP [kg C <sub>2</sub> H <sub>4</sub> -eq.]	0.730	0.0106	0.0684	0.00306	0.00306
ADPE [kg Sb-eq.]	8.78E-05	4.70E-06	4.70E-06	6.86E-08	6.86E-08
ADPF [MJ]	1,900	814	814	73.8	73.8

## Resource Use

**Table 9: Resource use, 1 m<sup>3</sup> of sawn, kiln-dried softwood.**

	Production	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
Parameter [Unit]	A1-A3	C4	C4	C3	C3
PERE [MJ]	1,910	57.2	57.2	0.488	0.488
PERM [MJ]	9,290	0	0	-9,290	-9,290
PERT [MJ]	11,200	57.2	57.2	-9,290	-9,290
PENRE [MJ]	1,440	826	826	73.9	73.9
PENRM [MJ]	0	0	0	0	0
PENRT [MJ]	1,440	826	826	73.9	73.9
SM [kg]	0.00208	0	0	0	0
RSF [MJ]	0	0	0	0	0
NRSF [MJ]	0	0	0	0	0
FW [m <sup>3</sup> ]	1.01	0.0124	0.0564	6.97E-04	6.97E-04

**PERE** = Use of renewable primary energy excluding renewable primary energy resources used as raw materials; **PERM** = Use of renewable primary energy resources used as raw materials; **PERT** = Total use of renewable primary energy resources; **PENRE** = Use of non-renewable primary energy excluding non-renewable primary energy resources used as raw materials; **PENRM** = Use of non-renewable primary energy resources used as raw materials; **PENRT** = Total use of non-renewable primary energy resources; **SM** = Use of secondary material; **RSF** = Use of renewable secondary fuels; **NRSF** = Use of non-renewable secondary fuels; **FW** = Net use of fresh water

**Table 10: Resource use, 1 m<sup>3</sup> of dressed, kiln-dried softwood.**

	Production	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
Parameter [Unit]	A1-A3	C4	C4	C3	C3
PERE [MJ]	2,340	57.2	57.2	0.488	0.488
PERM [MJ]	9,290	0	0	-9,290	-9,290
PERT [MJ]	11,600	57.2	57.2	-9,290	-9,290
PENRE [MJ]	1,910	826	826	73.9	73.9
PENRM [MJ]	0	0	0	0	0
PENRT [MJ]	1,910	826	826	73.9	73.9
SM [kg]	0.00235	0	0	0	0
RSF [MJ]	0	0	0	0	0
NRSF [MJ]	0	0	0	0	0
FW [m <sup>3</sup> ]	1.33	0.0124	0.0564	6.97E-04	6.97E-04

## Waste and Output Flows

**Table 11: Waste categories, 1 m<sup>3</sup> of sawn, kiln-dried softwood.**

	Production	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
Parameter [Unit]	A1-A3	C4	C4	C3	C3
HWD [kg]	0.0103	2.34E-06	2.34E-06	1.07E-07	1.07E-07
NHWD [kg]	23.2	552	455	0.00172	0.00172
RWD [kg]	0.00232	0.00458	0.00458	7.87E-06	7.87E-06
CRU [kg]	0	0	0	0	0
MFR [kg]	0	0	0	0	551
MER [kg]	0	0	0	551	0
EEE [MJ]	0	1.07	107	0	0
EET [MJ]	0	0	0	0	0


*HWD* = Hazardous waste disposed; *NHWD* = Non-hazardous waste disposed; *RWD* = Radioactive waste disposed;  
*CRU* = Components for reuse; *MFR* = Materials for recycling; *MER* = Materials for energy recovery;  
*EEE* = Exported electrical energy; *EET* = Exported thermal energy

**Table 12: Waste categories, 1 m<sup>3</sup> of dressed, kiln-dried softwood.**

	Production	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
Parameter [Unit]	A1-A3	C4	C4	C3	C3
HWD [kg]	0.0117	2.34E-06	2.34E-06	1.07E-07	1.07E-07
NHWD [kg]	29.8	552	455	0.00172	0.00172
RWD [kg]	0.00273	0.00458	0.00458	7.87E-06	7.87E-06
CRU [kg]	0	0	0	0	0
MFR [kg]	0	0	0	0	551
MER [kg]	0	0	0	551	0
EEE [MJ]	0	1.07	107	0	0
EET [MJ]	0	0	0	0	0

# Interpretation

## Understanding the Life Cycle of Softwood Timber

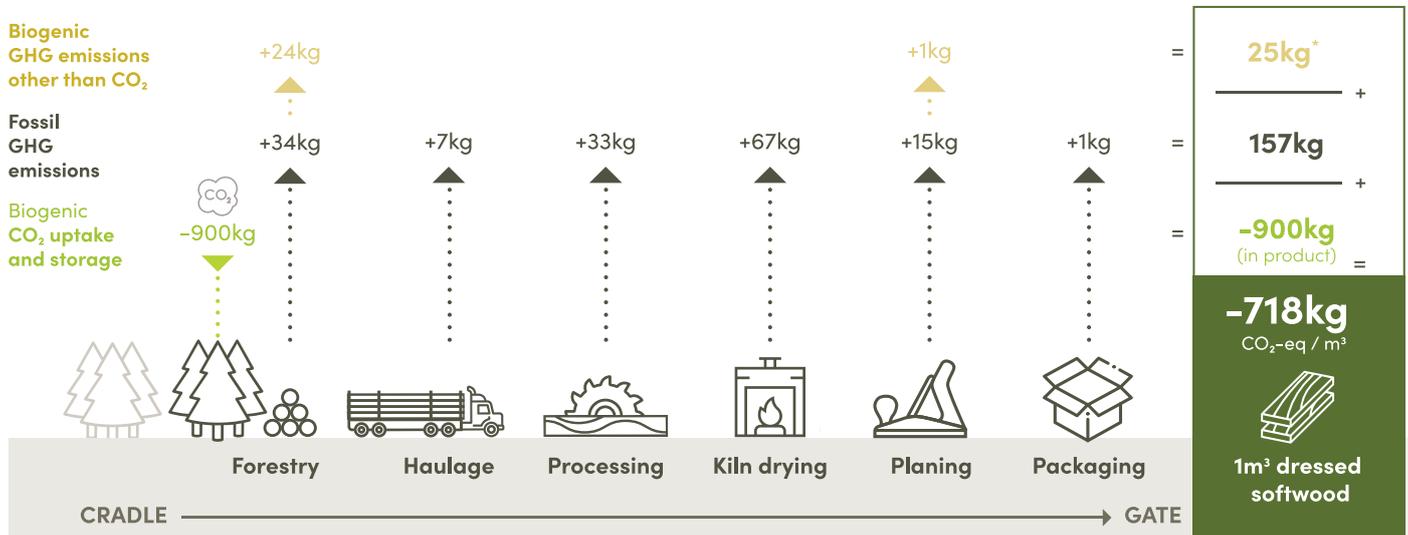

### Carbon footprint 1m<sup>3</sup> of KD dressed softwood

'Cradle to Gate' A1 - A3

\*CO<sub>2</sub> biogenic emissions from production (e.g. from combustion and degradation of residues) are excluded as they are balanced by uptake during tree growth (i.e., balance to zero)

## Variation in Results

The variation between sites used to create the average shown in this EPD are given in Table 13 for the environmental impact indicators in modules A1-A3.

**Table 13: Inter-site variability for softwood (modules A1-A3).**

Parameter [Unit]	Sawn, kiln-dried softwood			Dressed, kiln-dried softwood		
	Min	Max	CV	Min	Max	CV
GWP [kg CO <sub>2</sub> -eq.]	-7.7%	+7.0%	±5.5%	-11.8%	+10.1%	±7.9%
GWPF [kg CO <sub>2</sub> -eq.]	-51.5%	+47.2%	±36.9%	-54.6%	+47.0%	±36.6%
GWPB [kg CO <sub>2</sub> -eq.]	-0.1%	+0.1%	±0.1%	-0.2%	+0.1%	±0.1%
ODP [kg CFC11-eq.]	-28.0%	+46.9%	±27.2%	-33.8%	+59.4%	±33.1%
AP [kg SO <sub>2</sub> -eq.]	-33.3%	+14.0%	±15.6%	-34.6%	+14.0%	±16.6%
EP [kg PO <sub>4</sub> <sup>3-</sup> -eq.]	-13.2%	+6.3%	±6.5%	-13.8%	+6.2%	±6.8%
POCP [kg C <sub>2</sub> H <sub>4</sub> -eq.]	-7.2%	+4.5%	±4.2%	-7.4%	+4.5%	±4.1%
ADPE [kg Sb-eq.]	-1.1%	+6.6%	±2.9%	-1.0%	+6.4%	±2.6%
ADPF [MJ]	-51.2%	+59.3%	±44.9%	-54.0%	+53.4%	±43.5%

**Min** = (minimum - average) / average; **Max** = (maximum - average) / average;

**CV** = coefficient of variation = standard deviation / average

## Carbon Dioxide Sequestration

All major Australian production forests and plantations are independently certified to one, or both, of the internationally recognised forest management certification systems: the Australian Standard® for Sustainable Forest Management (AS 4708) of Responsible Wood which is recognised under the Programme for the Endorsement of Forest Certification (PEFC), and/or the Forest Stewardship Council's (FSC®) Australian National Forest Stewardship Standard. It is therefore appropriate to include biogenic CO<sub>2</sub> sequestration in this EPD in line with EN 16485 (Section 6.3.4.2).

For more information on certification by forest owner or manager please see:

<https://www.responsiblewood.org.au/search-database/> and

<https://info.fsc.org/certificate.php>

# Other Environmental Information

## Module D: Recycling, Reuse and Recovery Potentials

**Table 14: Module D, 1 m<sup>3</sup> of sawn, kiln-dried softwood.**

Parameter [Unit]	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
<b>Environmental Impact</b>				
GWP [kg CO <sub>2</sub> -eq.]	-0.275	-27.5	-614	-68.1
GWPF [kg CO <sub>2</sub> -eq.]	-0.275	-27.5	-615	-61.3
GWPB [kg CO <sub>2</sub> -eq.]	-1.46E-04	-0.0146	1.29	-6.82
ODP [kg CFC11-eq.]	-1.70E-15	-1.70E-13	-1.28E-14	-1.70E-13
AP [kg SO <sub>2</sub> -eq.]	-0.00110	-0.110	-0.0201	-0.418
EP [kg PO <sub>4</sub> <sup>3--</sup> -eq.]	-9.85E-05	-0.00985	-0.0424	-0.0976
POCP [kg C <sub>2</sub> H <sub>4</sub> -eq.]	-5.90E-05	-0.00590	0.0993	-0.317
ADPE [kg Sb-eq.]	-1.87E-08	-1.87E-06	-5.20E-05	-2.17E-05
ADPF [MJ]	-3.08	-308	-10,500	-782
<b>Resource Use</b>				
PERE [MJ]	-0.470	-47.0	-3.59	-1,890
PERM [MJ]	0	0	0	0
PERT [MJ]	-0.470	-47.0	-3.59	-1,890
PENRE [MJ]	-3.09	-309	-10,500	-783
PENRM [MJ]	0	0	0	0
PENRT [MJ]	-3.09	-309	-10,500	-783
SM [kg]	0	0	0	551
RSF [MJ]	0	0	9,290	0
NRSF [MJ]	0	0	0	0
FW [m <sup>3</sup> ]	-0.00148	-0.148	-0.00978	-0.454
<b>Wastes and Outputs</b>				
HWD [kg]	-5.00E-10	-5.00E-08	-2.42E-06	-3.95E-07
NHWD [kg]	-7.96E-04	-0.0796	25.9	-10.9
RWD [kg]	-5.28E-07	-5.28E-05	-7.17E-04	-5.39E-04
CRU [kg]	0	0	0	0
MFR [kg]	0	0	0	0
MER [kg]	0	0	0	0
EEE [MJ]	0	0	0	0
EET [MJ]	0	0	0	0

**Table 15: Module D, 1 m<sup>3</sup> of dressed, kiln-dried softwood.**

Parameter [Unit]	Landfill (typical)	Landfill (NGA)	Energy recovery	Recycling
<b>Environmental Impact</b>				
GWP [kg CO <sub>2</sub> -eq.]	-0.275	-27.5	-614	-68.1
GWPF [kg CO <sub>2</sub> -eq.]	-0.275	-27.5	-615	-61.3
GWPB [kg CO <sub>2</sub> -eq.]	-1.46E-04	-0.0146	1.29	-6.82
ODP [kg CFC11-eq.]	-1.70E-15	-1.70E-13	-1.28E-14	-1.70E-13
AP [kg SO <sub>2</sub> -eq.]	-0.00110	-0.110	-0.0201	-0.418
EP [kg PO <sub>4</sub> <sup>3--</sup> -eq.]	-9.85E-05	-0.00985	-0.0424	-0.0976
POCP [kg C <sub>2</sub> H <sub>4</sub> -eq.]	-5.90E-05	-0.00590	0.0993	-0.317
ADPE [kg Sb-eq.]	-1.87E-08	-1.87E-06	-5.20E-05	-2.17E-05
ADPF [MJ]	-3.08	-308	-10,500	-782
<b>Resource Use</b>				
PERE [MJ]	-0.470	-47.0	-3.59	-1,890
PERM [MJ]	0	0	0	0
PERT [MJ]	-0.470	-47.0	-3.59	-1,890
PENRE [MJ]	-3.09	-309	-10,500	-783
PENRM [MJ]	0	0	0	0
PENRT [MJ]	-3.09	-309	-10,500	-783
SM [kg]	0	0	0	551
RSF [MJ]	0	0	9,290	0
NRSF [MJ]	0	0	0	0
FW [m <sup>3</sup> ]	-0.00148	-0.148	-0.00978	-0.454
<b>Wastes and Outputs</b>				
HWD [kg]	-5.00E-10	-5.00E-08	-2.42E-06	-3.95E-07
NHWD [kg]	-7.96E-04	-0.0796	25.9	-10.9
RWD [kg]	-5.28E-07	-5.28E-05	-7.17E-04	-5.39E-04
CRU [kg]	0	0	0	0
MFR [kg]	0	0	0	0
MER [kg]	0	0	0	0
EEE [MJ]	0	0	0	0
EET [MJ]	0	0	0	0

## Durability and Preservative Treatment

As described in the Scope section, the body of the EPD covers untreated seasoned sawn softwood products. These products will deliver a long service life in most building, joinery and furniture applications when they are protected from termite attack and used inside a building envelope.

While the majority of seasoned sawn softwood produced in Australia for structural applications is untreated, a significant proportion is treated in the factory for termite and/or decay protection. Products to be used in outdoor applications such as decking, cladding, fencing and landscaping are usually treated to the appropriate hazard class. The following treatment types were used by the softwood producers participating in the survey and thus have been modelled:

Treatment	Hazard class
Bifenthrin	H2, H2F
Low organic solvent preservative (LOSP) (permethrin)	H2, H2F
Low organic solvent preservative (LOSP) (azole + permethrin)	H3
Copper chrome arsenic (CCA)	H3 & H4
Copper with didecyl dimethyl ammonium chloride or carbonate/bicarbonate (DDAX)	H3
Copper azole	H3 & H4

The values shown in Table 16 and Table 17 may be added to the A1-A3 values per m<sup>3</sup> of seasoned softwood given in Tables 7 to 12. This allows the associated A1-A3 impacts per m<sup>3</sup> of treated softwood to be calculated for each treatment type.

**Table 16: Environmental data for preservative treatment of softwood (non-copper treatments), per m<sup>3</sup> of treated wood**

Parameter [Unit]	Bifenthrin [H2]	Bifenthrin [H2F]	LOSP (permethrin) [H2]	LOSP (permethrin) [H2F]	LOSP (azole + permethrin) [H3]
<b>Environmental Impact</b>					
GWP [kg CO <sub>2</sub> -eq.]	10.8	10.5	11.8	11.0	58.6
GWPF [kg CO <sub>2</sub> -eq.]	10.8	10.5	11.7	11.0	58.5
GWPB [kg CO <sub>2</sub> -eq.]	0.0104	0.00820	0.0165	0.0119	0.0943
ODP [kg CFC11-eq.]	1.53E-12	8.99E-13	3.35E-12	2.00E-12	1.51E-10
AP [kg SO <sub>2</sub> -eq.]	0.0417	0.0409	0.0443	0.0425	0.151
EP [kg PO <sub>4</sub> <sup>3-</sup> -eq.]	0.00379	0.00370	0.00408	0.00388	0.0140
POCP [kg C <sub>2</sub> H <sub>4</sub> -eq.]	0.0384	0.0228	0.0188	0.0120	6.74
ADPE [kg Sb-eq.]	2.67E-05	1.55E-05	8.73E-05	5.18E-05	1.75E-04
ADPF [MJ]	145	135	159	144	2,062
<b>Resource Use</b>					
PERE [MJ]	18.0	17.6	20.1	18.8	37.6
PERM [MJ]	0	0	0	0	0
PERT [MJ]	18.0	17.6	20.1	18.8	37.6
PENRE [MJ]	145	136	161	145	2,081
PENRM [MJ]	0	0	0	0	0
PENRT [MJ]	145	136	161	145	2,081
SM [kg]	0	0	0	0	0
RSF [MJ]	0	0	0	0	0
NRSF [MJ]	0	0	0	0	0
FW [m <sup>3</sup> ]	62.7	58.8	62.5	58.9	216
<b>Wastes and Outputs</b>					
HWD [kg]	3.12E-08	2.58E-08	5.48E-08	4.01E-08	3.50E-07
NHWD [kg]	0.0372	0.0336	0.0516	0.0423	0.312
RWD [kg]	2.67E-04	1.60E-04	7.20E-04	4.33E-04	0.00762
CRU [kg]	0	0	0	0	0
MFR [kg]	0	0	0	0	0
MER [kg]	0	0	0	0	0
EEE [MJ]	0	0	0	0	0
EET [MJ]	0	0	0	0	0

**Table 17: Environmental data for preservative treatment of softwood (copper treatments), per m<sup>3</sup> of treated wood.**

Parameter [Unit]	Copper + DDAX [H3]	Copper azole [H3]	Copper azole [H4]	CCA [H3]	CCA [H4]
<b>Environmental Impact</b>					
GWP [kg CO <sub>2</sub> -eq.]	17.4	14.9	18.8	32.2	24.7
GWPF [kg CO <sub>2</sub> -eq.]	17.4	14.8	18.8	32.1	24.7
GWPB [kg CO <sub>2</sub> -eq.]	0.0530	0.0365	0.0621	0.0832	0.0570
ODP [kg CFC11-eq.]	8.72E-11	5.72E-11	1.04E-10	8.19E-14	7.50E-14
AP [kg SO <sub>2</sub> -eq.]	0.319	0.223	0.373	0.339	0.238
EP [kg PO <sub>4</sub> <sup>3-</sup> -eq.]	0.00613	0.00525	0.00662	0.0104	0.00811
POCP [kg C <sub>2</sub> H <sub>4</sub> -eq.]	0.0144	0.0102	0.0167	0.0162	0.0114
ADPE [kg Sb-eq.]	2.59E-04	1.70E-04	3.08E-04	0.00280	0.00186
ADPF [MJ]	274	222	304	386	297
<b>Resource Use</b>					
PERE [MJ]	23.6	21.3	24.9	26.4	23.3
PERM [MJ]	0	0	0	0	0
PERT [MJ]	23.6	21.3	24.9	26.4	23.3
PENRE [MJ]	280	226	310	394	303
PENRM [MJ]	0	0	0	0	0
PENRT [MJ]	280	226	310	394	303
SM [kg]	0	0	0	0	0
RSF [MJ]	0	0	0	0	0
NRSF [MJ]	0	0	0	0	0
FW [m <sup>3</sup> ]	98.2	82.8	107	105	87.7
<b>Wastes and Outputs</b>					
HWD [kg]	4.76E-04	3.12E-04	5.67E-04	2.00E-07	1.39E-07
NHWD [kg]	0.163	0.117	0.189	1.39	0.933
RWD [kg]	0.00214	0.00141	0.00255	0.00336	0.00223
CRU [kg]	0	0	0	0	0
MFR [kg]	0	0	0	0	0
MER [kg]	0	0	0	0	0
EEE [MJ]	0	0	0	0	0
EET [MJ]	0	0	0	0	0

## Water Consumption

The “FW” indicator in the EPD results tables reports consumption (i.e. net use) of ‘blue’ water (which includes river water, lake water and ground water). This indicator deliberately excludes consumption of ‘green’ water (rain water).

PCR 2012:01 (Section 16.1) states that all water loss from a drainage basin is considered consumption, including any net loss of rain water. According to the PCR, net loss should be interpreted as any additional water loss beyond what would occur in the original, natural system. For plantation softwood forestry, the natural system might be a native forest or a grassland (Quinteiro et al. 2015).

The initial versions of this EPD (v1.0 and v1.1) included estimated losses of rain water in the main results tables, labelled as green water consumption. These values were based on calculated differences in water flow between plantation forests and a base case land use (pasture) from the original CSIRO LCI study (CSIRO 2009).

Table 18 reports green water consumption calculated by CSIRO using 2005-08 data. These values have not been updated and are now reported here rather than in the main results tables to reflect their uncertainty. At the time of writing, there is no internationally agreed method for calculating green water consumption due to evapotranspiration relative to a hypothetical natural state (Manzardo et al. 2016). As such, different calculation methods may yield significantly different results, introducing a high level of uncertainty.

The reader should also be aware that water consumption does not account for relative water stress in the catchment(s) where the forest is located, meaning that it provides no information about the potential impacts of any water consumption that does occur.

**Table 18: Green water consumption estimates for modules A1-A3 from CSIRO (2009).**

	Sawn, kiln-dried softwood	Dressed, kiln-dried softwood
Parameter [Unit]	A1-A3	A1-A3
Green water consumption in forest [m <sup>3</sup> ]	291	356

## Timber & Forest Certification

Many Australian timber and reconstituted wood products are certified to a forest certification scheme. This certification is an independent auditing process which provides:

- Assurance that the timber is from well-managed forests certified to internationally and nationally accepted forest management standards
- Assurance that the timber is from legally harvested sources
- Chain of custody (CoC) certification extending from the forest to the end user, which is traceable throughout the supply chain.

Two schemes apply to Australian wood production forests. One is administered by Responsible Wood whose Australian Standard® for Sustainable Forest Management (AS 4708) is endorsed by the international Programme for Endorsement of Forest Certification (PEFC). The other scheme is administered by the Forest Stewardship Council (FSC®).

If a Green Star project elects to use the timber credit as part of their Green Star submission, the Green Building Council of Australia recognises PEFC-endorsed forest certification schemes (such as Responsible Wood) as well as FSC. Compliance with the chain of custody certification rules of either forest certification scheme for at least 95% by value of timber products used in the project will meet the requirements for credit (GBCA 2014).

There are 11.3 million hectares of native and plantation forests certified under Responsible Wood’s sustainable forest management standard (PEFC 2020) and 1.2 million hectares certified under FSC’s national Australian standard (FSC 2019). In addition, many Australian softwood manufacturers’ premises listed in this EPD are chain of custody certified under one or both schemes so they can supply products with a valid certification claim.

## Land Use and Biodiversity

Like other land uses, forestry operations for timber and wood production can have both positive and negative effects on biodiversity. However, as biodiversity varies considerably by region and as data are often limited, assessing potential biodiversity impacts within LCA is challenging.

An Australian study completed shortly before initial publication of this EPD (Turner et al. 2014) demonstrated a new method – BiolImpact – to discern the biodiversity impacts of different land uses. A trial of this method was conducted using case studies in three different regions and four production systems in New South Wales: native hardwood forestry, plantation softwood forestry, mixed cropping and rangeland grazing. Managed forestry resulted in biodiversity impacts equivalent to or better than those of cropping/grazing systems.

# References

- ABARES. (2019). *Australia's forests at a glance 2019: with data to 2017-18*. Australian Bureau of Agricultural and Resource Economics, Canberra, November. CC BY 4.0. Available <https://www.agriculture.gov.au/abares/forestsaustralia/australias-forests-at-a-glance>
- AFS. (2017) Australian Forestry Standard Ltd. Available at <http://www.forestrystandard.org.au/>
- AS 1604.1:2010. *Specification for preservative treatment—Part 1: Sawn and round timber*. Standards Australia.
- Australian Government. (2021). *National Inventory Report 2019, Volume 3*. Australian National Greenhouse Accounts. Available at <https://www.industry.gov.au/data-and-publications/national-greenhouse-accounts-2019/national-inventory-report-2019>
- Australian Government. (2014a). *National Greenhouse Accounts Factors* - December 2014. Department of Environment.
- Australian Government. (2014b). *Technical Guidelines for the Estimation of Greenhouse Gas Emissions by Facilities in Australia*. Department of Environment.
- Australian Government. (2020). *National Greenhouse Accounts Factors – September 2020*. Department of Environment.
- Australian Government. [2021]. *National Inventory Report 2019 Volume 2*. Australian Government Department of Industry, Science, Energy and Resources.
- Barlaz, M. (1998). Carbon storage during biodegradation of municipal solid waste components in laboratory scale landfills. *Global Biogeochemical Cycles*, 12 (2), 373–380.
- Blue Environment. (2013). *Analysis of landfill survey data*. Final report prepared for Waste Management Association of Australia. Available at <http://www.environment.gov.au/protection/national-waste-policy/publications/analysis-landfill-survey-data>
- Carre, A. (2011). *A Comparative Life Cycle Assessment of Alternative Constructions of a Typical Australian House Design*. Melbourne: Forest & Wood Products Australia. Available at [http://www.fwpa.com.au/images/marketaccess/PNA147-0809\\_Research\\_Report\\_Comparative-LCA\\_0.pdf](http://www.fwpa.com.au/images/marketaccess/PNA147-0809_Research_Report_Comparative-LCA_0.pdf)
- Commonwealth of Australia. (2020). *National Inventory Report 2019 Volume 2*.
- CSIRO. (2009). (Prepared by Tucker, S.N.; Tharumarajah, A.; May, B.; England, J.; Paul, K.; Hall, M.; Mitchell, P.; Rouwette, R.; Seo, S. and Syme, M.) *Life Cycle Inventory of Australian Forestry and Wood Products*. Prepared by the Commonwealth Scientific and Industrial Research Organisation on behalf of Forest and Wood Products Australia. Project number PNA008-0708.
- Downham, R., Gavran, M. and Frakes, I. (2019) ABARES National Wood Processing Survey 2016–17. ABARES Technical report 19.3, Canberra, June. CC BY 4.0. Available <https://agriculture.gov.au/abares/research-topics/forests/forest-economics>
- EN 15804:2012+A1:2013. *Sustainability of construction works – Environmental product declarations – Core rules for the product category of construction products*. Brussels: European Committee for Standardization.
- EN 16449:2014. *Wood and wood-based products – Calculation of the biogenic carbon content of wood and conversion to carbon dioxide*. Brussels: European Committee for Standardization.
- EN 16485:2014. *Round and sawn timber – Environmental Product Declarations – Product category rules for wood and wood-based products for use in construction*. Brussels: European Committee for Standardization.

- FSC (2019) FSC Australia Annual Report 2018. Available <https://au.fsc.org/en-au/newsroom/events/2019-agm>
- Forsythe Consultants. (2007). *Mapping the Timber Waste Stream from Building Demolition*. Available at [http://www.timberstewardship.org.au/images/pdf\\_documents/demolition\\_waste\\_barriers\\_final.pdf](http://www.timberstewardship.org.au/images/pdf_documents/demolition_waste_barriers_final.pdf)
- Gavran, M. (2020). *Australian forest and wood products statistics datasets 2020*, ABARES technical report, Canberra, November, CC BY 4.0. Available <https://www.agriculture.gov.au/abares/research-topics/forests/forest-economics/forest-wood-products-statistics>
- GBCA. (2014). *Revised Timber Credit*. Green Building Council of Australia. Available at <https://www.gbca.org.au/green-star/technical-support/materials-category/revised-timber-credit/2693.htm>
- Gifford, R. (2000). *Carbon Contents of Above-Ground Tissues of Forest and Woodland Trees*. Technical report No. 22. National Carbon Accounting Scheme. Australian Greenhouse Office. Available at <http://pandora.nla.gov.au/pan/23322/20020220-0000/www.greenhouse.gov.au/ncas/files/pdfs/tr22final.pdf>
- Houghton, J. (2015). *FWPA Data Aggregation Program: Softwood Data Series Market Coverage Reconciliation: Discussion Paper*. Forest & Wood Products Australia.
- IEPDS. (2020). PCR 2012:01, Construction products and Construction services (EN 15804:2012+A1:2013), Version 2.33, 2020-09-18. Stockholm: International EPD® System. Available at: <http://www.environdec.com/>
- ISO 14025:2006. *Environmental labels and declarations — Type III environmental declarations - Principles and procedures*. Geneva: International Organization for Standardization.
- Manzardo, A., Mazzi, A., Loss, A., Butler, M., Williamson, A. and Scipioni, A. (2016). *Lessons learned from the application of different water footprint approaches to compare different food packaging alternatives*. *Journal of Cleaner Production*, 112, pp. 4657-4666.
- National Timber Product Stewardship Group. (2015). Available at [www.timberstewardship.org.au](http://www.timberstewardship.org.au)
- PEFC (2020) PEFC Global Statistics. Data: December 2020. Available <https://www.pefc.org/discover-pefc/facts-and-figures>
- Quinteiro, P., Dias, A. C., Silva, M., Ridoutt, B. G., & Arroja, L. (2015). *A contribution to the environmental impact assessment of green water flows*. *Journal of Cleaner Production*, 93, 318-329.
- Sphera. (2020). *GaBi Database 2020 Life Cycle Inventory Documentation*. Chicago, United States. URL: <http://www.gabi-software.com/support/gabi/gabi-database-2020-lci-documentation/>
- Turner, P., Ximenes, F., Penman, T., Law, B., Waters, C., Mo, M. and Brock, P. (2014). *Accounting for biodiversity in Life Cycle Impact Assessments of forestry and agricultural systems – the BiolImpact metric*. Research report for Forest & Wood Products Australia Limited. Available at <http://www.fwpa.com.au>
- Wang, W., Padgett, J., De La Cruz, F. and Barlaz, M. (2011). *Wood biodegradation in laboratory-scale landfills*. *Environmental Science & Technology*, 45(16), pp. 6864-6871.
- WoodSolutions. (2012). *Timber Service Life Design Guide*. Available at <https://www.woodsolutions.com.au/Articles/Resources/Timber-Service-life-design>
- WoodSolutions. (2015). *Timber Preservation*. Available at <http://www.woodsolutions.com.au/Articles/Resources/Timber-Preservation>
- WPV. (2009). *Structural Timber Products Guide*. Wood Products Victoria. Available at <http://wpv.org.au/downloadable-resources/>
- Ximenes, F., Brooks, P., Wilson, C. and Giles, D. (2013). *Carbon Storage in Engineered Wood Products in Landfills*. Forest and Wood Products Australia. Available at <http://www.fwpa.com.au/rd-and-e/processing/181-carbon-storage-in-engineered-wood-products-in-landfills.html>

# WoodSolutions. Your information solution.



## Website

- Technical Design Guides
- Fire Test Reports
- Case studies
- Event Calendar
- Expert Advice

## Free Webinars & Podcasts

- **Free Webinars Tuesday 1100AEST**
- CPD points available (webinars)
- Local and international presenters
- A wide range of topics
- Recordings on the website



# Build your timber reference library with free Technical Guides

50,000+  
free  
technical  
downloads  
a year



## Updates and new titles ensure currency

The result of input from industry specialists and years of research, WoodSolutions technical design guides give you instant access to a comprehensive reference library.

Over 50 guides cover aspects ranging from design to durability, specification to detailing. Including worked drawings, they are an invaluable resource for ensuring timber-related projects comply with the National Construction Code (NCC).

Recent guides also cover the latest NCC code changes relating to height provisions for timber-framed and massive timber buildings. New titles are being added all the time.

**Discover more at [WoodSolutions.com.au](http://WoodSolutions.com.au)  
The website for wood.**

**Wood  
Solutions™**  
design and build  
[woodsolutions.com.au](http://woodsolutions.com.au)